

DEVELOPMENT AND *IN VITRO* EVALUATION OF PHYTOSOMES OF NARINGIN

JEEVANA JYOTHI B*, MARY RAGALATHA P

Department of Pharmaceutics, Institute of Pharmaceutical Technology, Sri Padmavati Mahila Visvavidyalayam (Women's University), Tirupati - 517 502, Andhra Pradesh, India. Email: jeevanajyothib8@gmail.com

Revised: 16 June 2019, Revised and Accepted: 27 July 2019

ABSTRACT

Objective: Phytosomes are novel herbal formulations meant for design of poorly soluble flavonoids of therapeutic potential. Naringin is a flavanone with poor oral absorption and bioavailability but possess antioxidant, anti-inflammatory, antiapoptotic, anti-ulcer, antiosteoporotic, and anticarcinogenic effects. Hence, the objective of the present work is the development of phytosomes of naringin to enhance its dissolution so that its therapeutic effects can be exploited.

Materials and Methods: Phytosomes containing 350 mg of naringin were prepared by antisolvent precipitation method and rotary evaporation method using soya lecithin as main polymer. The prepared phytosomes were evaluated by entrapment efficiency, *in vitro* drug release studies, and drug-excipient interaction studies.

Results: Phytosomes made by rotary evaporation method evidenced higher dissolution values than phytosomes made by antisolvent precipitation. Formulation F7 containing 350 mg of naringin and 1400 mg of soya lecithin revealed the highest percentage release of $84.5 \pm 0.39\%$ in 60 min and $99.7 \pm 0.24\%$ in 120 min. The percentage of drug entrapment efficiency values was satisfactory. Fourier-transform infrared spectroscopy spectra of pure naringin and naringin phytosomes revealed no interaction between the drug and polymers used for preparation.

Conclusion: Naringin phytosomes are produced successfully by the rotary evaporation method. Phytosomes made with 350 mg of naringin and 1400 mg of soya lecithin by rotary evaporation method are spherical with a rough outer surface and optimum release characteristics of 84.5 ± 0.39 in 60 min to possess optimum bioavailability and 99.7% in 120 min.

Keywords: Naringin, Flavonoid, Anticancer and Antioxidant, Poor bioavailability, Phytosomes, *In vitro* dissolution.

© 2019 The Authors. Published by Innovare Academic Sciences Pvt Ltd. This is an open access article under the CC BY license (<http://creativecommons.org/licenses/by/4.0/>) DOI: <http://dx.doi.org/10.22159/ajpcr.2019.v12i9.34798>

INTRODUCTION

Naringin is a flavanone glycoside found in citrus fruits and mainly in grapefruit juice. It is used in Chinese herbal medicine as an active ingredient of *Rhizoma Drynariae* [1]. It is responsible for bitter taste of fruits. It is reported to possess important pharmacological activities such as antioxidant, anti-inflammatory, antiapoptotic, anti-ulcer, antiosteoporotic, and anticarcinogenic effects [2]. In humans, naringin is metabolized to aglycone naringenin by enzyme naringinase present in the gut. This happens in two steps; naringin is hydrolyzed by L-rhamnosidase activity of naringinase to rhamnose and prunin. The prunin formed is then hydrolyzed by the d-glucosidase activity of naringinase into naringenin and glucose.

Many of the bioactive constituents of phytomedicines are flavonoids and have poor oral absorption [3-5]. Naringin also has lower absorption and bioavailability due to two factors. These chief constituents are the number of ringed molecule and not too much small that it will absorb by the diffusion process. The second factor is that flavonoid molecule or chief constituent of polyphenols has poor solubility with lipids. These are limitations that inhibit their absorption through the biological membrane [6]. To overcome these limitations and to exploit the therapeutic benefits of flavonoids, herbal drug design and technological products such as phytosomes are recently introduced and developed. The term "phyto" means plant, while "some" means cell-like. Phytosomes are also known as herbosomes [7]. It is a complex of natural active ingredient and a phospholipid mostly lecithin. These little cells protect plant extract or its active constituent from destruction by gastric secretions and gut bacteria due to gastroprotective property of phosphatidylcholine. It is claimed that phytosomes increase the absorption of conventional herbal extracts [8]. Some herbal compounds binding to phosphatidylcholine produce highly bio available form

of herbal compounds. Hence, phytosomes improve the absorption, increasing bioavailability and enhancing delivery to the tissue [9-11].

Literature reveals that there are no formulations of naringin as phytosomes. Hence, the present research work is aimed at production of phytosomes of naringin with enhanced dissolution with optimum drug release characteristics so that the product will have optimum absorption and bioavailability.

MATERIALS AND METHODS

Naringin and soya lecithin were purchased from HiMedia Pvt. Ltd. Methanol and dichloromethane were purchased from Sigma Aldrich Pvt. Ltd. n-Hexane was from SDL laboratories and all other chemicals used in the study were of analytical grade.

Preparation of phytosomes of naringin

Phytosomes of naringin were prepared by antisolvent precipitation method and rotary evaporation method.

Antisolvent precipitation method

Various ratios of naringin and soya lecithin were used to prepare naringin phytosomes by antisolvent precipitation method. Formulations with which discrete particles are not obtained are discarded, and three formulations (F1 to F3) successful in producing discrete particles are given in Table 1. During preparation, naringin and soya lecithin were placed in 100 ml round-bottomed flask and refluxed with dichloromethane for 2 h. When the solution was concentrated to 5-10 ml, 30 ml of n-hexane was added to get the complex as a precipitate. The precipitate was collected and placed in a desiccator for 24 h. The dried precipitate was crushed in mortar and sieved through #100 mesh. Powdered complex was placed in amber-colored glass bottle and was stored at room temperature.

Table 1: Composition of naringin phytosomes made by antisolvent precipitation method

Formulation code	Drug (mg)	Soya lecithin (mg)	Dichloromethane (ml)	n-hexane (ml)
F1	350	350	30	10
F2	350	700	30	10
F3	350	1050	30	10

Table 2: Composition of naringin phytosomes made by rotary evaporation method

Formulation code	Drug (mg)	Soya lecithin (mg)	Methanol (ml)	Dichloromethane (ml)	pH 7.4 phosphate buffer (ml)
F4	350	350	30	20	25
F5	350	700	30	20	25
F6	350	1050	30	20	25
F7	350	1400	30	20	25

Table 3: Entrapment efficiency of naringin phytosomes

Formulation code	% EE
F1	72.34±0.09
F2	81.17±0.21
F3	83.64±0.19
F4	91.91±0.44
F5	91.31±0.14
F6	90.01±0.21
F7	92.91±0.11

*n=3 ± S.D

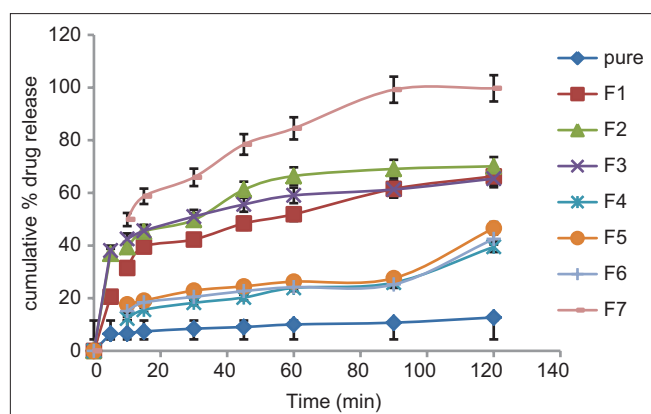


Fig. 1: Dissolution curves of naringin and naringin phytosomes F1 to F7

Rotary evaporation method

Five trials of naringin formulations were tried rotary evaporation method and their composition is given in Table 2. Various ratios of naringin to soya lecithin, namely 1:1, 1:2, 1:3, 1:4, and 1:5, were taken in the compositions, as shown in Table 1.

Accurately weighed quantity of naringin (drug) was dissolved in methanol and soya lecithin was dissolved in dichloromethane. The mixture of two solutions was transferred to round-bottomed flask and refluxed for 2 h (60°C). At this stage, the solution was obtained in a clear yellow color solution. The mixture was taken in RBF and evaporated in a rotary evaporator at 60°C until all solvents evaporated perfectly and a thin film was produced. The thin film was hydrated with phosphate buffer 7.4, and the suspension was filtered, collected, and dried under vacuum and was stored in amber color bottles.

In vitro evaluation of prepared phytosomes

Drug entrapment efficiency

The percentage of drug entrapment efficiency was determined for all the prepared naringin phytosomes (F1 to F7). 100 mg of the product was weighed and transferred into 100 ml volumetric flask containing

100 ml of phosphate buffer (pH 6.8) and was kept it aside. On the next day, the volumetric flask was kept for continues stirring for 2 h at 35°C to complete release of drug from the formulation. Then, the solution was filtered, and 1 ml sample was diluted to 10 ml and analyzed for the drug entrapment efficiency using ultra violet (UV) spectrophotometer at 262 nm. Drug entrapment was calculated using the formula.

$$\text{Percentage drug entrapment efficiency} = \frac{\text{Actual drug content}}{\text{Theoretical content}} \times 100$$

In vitro drug release studies

In vitro dissolution studies were carried for pure naringin and also for prepared naringin phytosomes (F1 to F7) using USP Type II dissolution test apparatus (Labindia DS 8000, India). 900 ml of pH 7.4 phosphate buffer maintained at 37±0.5°C temperature and 100 rpm was used as a dissolution medium. Phytosomes equivalent to contain 350 mg of naringin was placed in the medium. At predetermined time intervals, 5 ml of each sample was withdrawn at regular time intervals (0, 5, 10, 20, 30, 45, 60, 90, and 120 min) and was replaced by an equal volume of fresh medium. The samples were filtered and diluted and analyzed on UV spectrophotometer (Shimadzu, UV 1700) at 283 nm.

Assessment of drug release kinetics

Rate and mechanism of drug release from matrix tablets was assessed by fitting the data into zero-order kinetics [Q=K₀ t], first-order kinetics [log Q=Log Q₀+K₁ t/2.303], Higuchi's model [Q=KH t^{1/2}], and Korsmeyer-Peppas model [F=(Mt/M)=K t_n].

Phase-contrast microscopy of naringin phytosomes

For determination of the shape of naringin phytosomes, small amount of phytosomes are kept on the glass slide and spread over the slide. Then, the microscopy was adjusted to ×10 and focusing on the slide by adjusting the stage micrometer. Then, the shape of the phytosomes was observed on the screen and the photograph was taken.

Fourier-transform infrared spectroscopy (FTIR) of naringin phytosomes

Drug excipient interaction between the naringin and the ingredients used for design of phytosomes was investigated by FTIR by potassium bromide pressed pellet technique (Bruker, Japan). The FTIR spectrum was obtained for pure naringin and for phytosomes of naringenin transmittance mode in the range of 400–4000 cm⁻¹.

RESULTS AND DISCUSSION

Phytosomes of naringin were produced successfully by both the selected methods such as antisolvent precipitation method (F1, F2, and F3) and rotary evaporation method (F4 to F7). All formulations (F1 to F7) were subjected to *in vitro* evaluation by %entrapment efficiency, drug release studies, and release kinetics. Promising formulation with enhanced dissolution rate was investigated by phase-contrast microscopy to identify appearance and by drug-excipient interaction studies by FTIR.

Table 4: % Drug dissolved versus time values of pure naringin and naringin phytosomes (F1 to F7)

Time (min)	Pure drug	F1	F2	F3	F4	F5	F6	F7
5	6.48±0.21	20.6±0.18	36.9±0.25	38.1±0.34	7.7±0.22	10.35±0.51	9.35±0.21	35.5±0.21
10	6.61±0.12	31.5±0.35	39.4±0.34	42.5±0.19	12.3±0.43	17.7±0.42	15.1±0.63	49.9±0.12
15	7.38±0.35	39.6±0.24	45.3±0.16	45.6±0.21	15.6±0.32	19.1±0.42	18.4±0.11	58.7±0.35
30	8.43±0.18	42.3±0.48	49.7±0.18	51.01±0.24	18.25±0.75	22.9±0.35	20.5±0.44	65.9±0.58
45	9.06±0.36	48.4±0.15	61.2±0.17	55.6±0.15	20.27±0.42	24.5±0.28	22.7±0.43	78.4±0.35
60	10.03±0.55	51.9±0.14	66.4±0.27	59.05±0.26	23.9±0.51	26.3±0.15	24.2±0.41	84.5±0.39
90	10.71±0.24	61.5±0.19	69.1±0.22	61.3±0.34	25.9±0.30	27.6±0.89	25.2±0.62	99.2±0.22
120	12.69±0.3	66.3±0.28	70.1±0.37	65.4±0.33	39.5±0.23	46.6±0.21	42.5±0.11	99.7±0.24

*n=3 ± S.D

Table 5: Data of drug release kinetics plots

Time (min)	% Cumulative drug release	Log% Cumulative drug release	% Drug retained	Log % drug retained	Log T	√T	³ √T
0	0	0	100	2	0	0	0
5	35.5	1.5502	64.5	1.809	0.698	2.23	1.709
10	49.9	1.6981	50.1	1.699	1	3.16	2.154
15	58.7	1.7686	41.3	1.615	1.176	3.87	2.466
30	65.9	1.8188	34.1	1.532	1.477	5.47	3.107
45	78.4	1.8943	21.6	1.334	1.653	6.70	3.556
60	84.5	1.9268	15.5	1.190	1.778	7.745	3.914
90	99.2	1.9965	0.8	0.096	1.954	9.48	4.481
120	99.7	1.9986	0.3	0.522	2.079	10.95	4.932

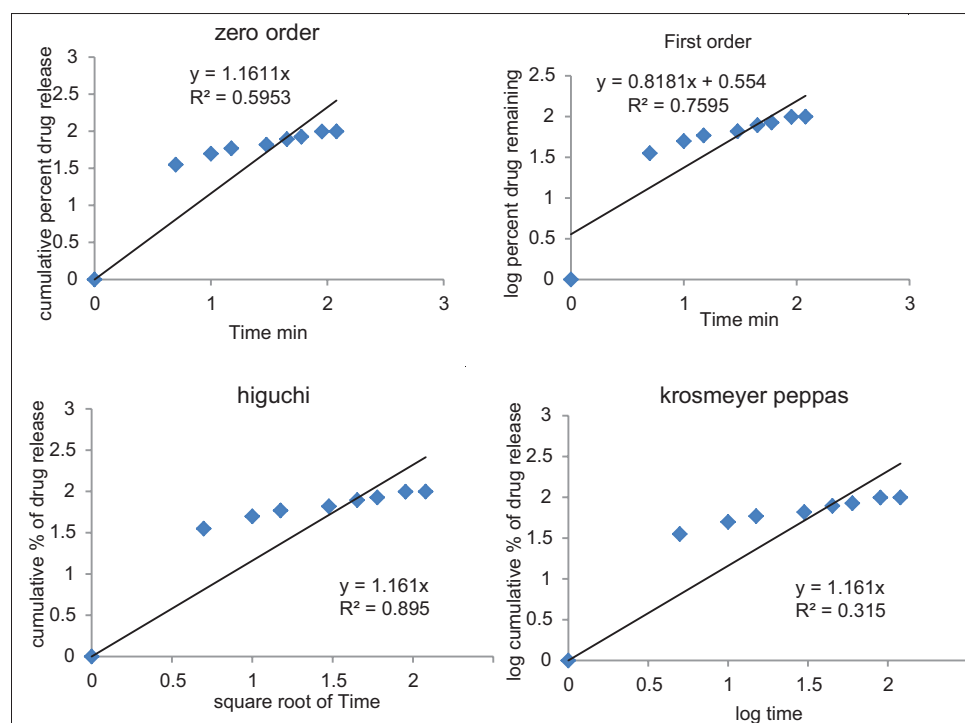


Fig. 2: Kinetic plots of drug release from naringin phytosomes F7

Drug entrapment efficiency

Drug entrapment efficiency values of prepared phytosomes of naringin, F1 to F7, are shown in Table 3 and are found satisfactory in all the formulations. However there better value with formulations made by rotary evaporation method F4 to F7.

In vitro drug release studies

The results of *in vitro* drug release studies of pure naringin and phytosomes of naringin made by antisolvent precipitation method (F1 to F3) and rotary evaporation method (F4 to F7) are shown in Fig. 1 and Table 4. Pure drug evidenced only 12.69% in 120 min, indicating poor solubility of naringin. However, there is enhancement of drug

dissolution when it is made as phytosomes. Phytosomes made by rotary evaporation method (F4 to F7) evidenced higher dissolution values than phytosomes made by antisolvent precipitation (F1 to F3). Formulation F7 exhibited the highest percentage as 84.5±0.39 in 60 min and 99.7±0.24% in 120 min. Hence, this was considered as promising formulation and was further investigated for drug-excipient interaction studies.

Drug release kinetics of naringin phytosomes

Drug release kinetics of promising formulation (F7) was assessed by plotting zero-order, first-order, Higuchi, and Korsmeyer-Peppas (k-p) plots. The corresponding data and the plots are shown in Table 5 and

